

The Oxidation of Toluene on Various Molybdenum-Containing Catalysts

N. K. NAG,¹ T. FRANSEN, AND P. MARS

Twente University of Technology, Department of Chemical Technology, P.O. Box 217, Enschede 7500 AE, The Netherlands

Received April 11, 1980

The activities for the vapour-phase oxidation of toluene of various molybdenum-containing catalysts have been measured in a flow microreactor operating at 1 atm pressure. The catalysts comprised (a) unsupported crystalline MoO₃, (b) Mo oxide monolayers on Al₂O₃, CeO₂, TiO₂, and ZrO₂ supports, and (c) Al-, Ce-, and Zr-molybdate salts. The rates of oxidation of toluene per unit surface area on the monolayer catalysts are higher than those on the corresponding salts, but the selectivities for the partial oxidation products show the opposite trend. The catalytic behaviour of unsupported MoO₃ resembles more closely that of the salts than that of the monolayer catalysts. The kinetic data for the oxidation of toluene on all catalysts can be interpreted on the basis of a reduction-oxidation mechanism. The energies of activation for the reduction and oxidation steps are correlated with the ionic potentials of the cations in the supports. Poisoning by pyridine of MoO₃/TiO₂ has a profound effect on the activity and selectivity of the monolayer catalyst and gives some information about the nature and concentration of the active sites.

INTRODUCTION

The large influence of foreign ions on the catalytic behaviour of molybdenum oxide is well known. Higher activity and improved selectivity for the partial oxidation of olefins are generally achieved by using MoO₃ promoted with Bi₂O₃ or SnO₂ rather than the pure oxide alone (1-4).

The activities of the catalysts containing molybdenum oxide have been correlated with the rates of isotopic homomolecular and heteromolecular exchange of oxygen (4-7), as well as with the reduction by hydrogen (2, 8). The selectivity of these catalysts has been suggested as being connected with the basic (9) and acidic (3, 10) properties of the added component or with the different types of metal-oxygen bonds on the surface (11). The selectivity for the partial oxidation products is higher with catalysts containing metal-oxygen double

bonds (12, 13). Total oxidation is relatively more extensive when this bond is weaker (6, 8, 14) and predominates with oxides where oxygen is bridged between metal ions.

The purpose of this work has been to study the modifying effect of various metal oxides on the behaviour of molybdenum oxide towards the oxidation of toluene and to establish the influence of these oxides on the rates and activation energies of the oxidation and reduction steps. A systematic comparison has also been made of the catalytic behaviour of the so-called molybdenum oxide monolayer catalysts and of the three-dimensional molybdate salts with that of crystalline MoO₃.

EXPERIMENTAL

Catalysts

The supports used were either commercial products or were prepared in our laboratory (see Table 1).

CeO₂ was prepared by heating Ce(NO₃)₃ (E. Merck, Analar) in air at 500°C for 2 h (15). ZrO₂ was prepared by precipitation of

¹ Present address: Fritz-Haber-Institut der Max-Planck-Gesellschaft zur Förderung der Wissenschaften B. V. Faradayweg 4-6, 1 Berlin 33/Dahlem, Germany.

TABLE 1
Summary of the Methods of Preparation and Properties of Various Catalysts

Catalysts	Source or method of preparation	Calcination temperature (°C)	Specific surface area (m ² · g ⁻¹)	MoO ₃ content (g/g) × 100	Surface area per MoO ₃ unit (Å ²)
1. Carriers					
CeO ₂	Ref. (15)	500	70.0		
ZrO ₂	Ref. (16)	380	125.0	—	—
TiO ₂	Degussa TiO ₂	—	47.0		
Al ₂ O ₃	Degussa Al ₂ O ₃	—	72.0		
2. MoO ₃					
	Ref. (17)	340	3.6		
3. Monolayer catalysts					
MoO _x /CeO ₂	Liquid-phase adsorption	500	67.0	8.8	18.2
MoO _x /ZrO ₂	of molybdate ions on the	500	125.0	10.6	28.2
MoO _x /TiO ₂	support oxides, see Ref.	500	46.0	6.1	18.0
MoO _x /Al ₂ O ₃	(18) for details	500	72.0	10.2	17.9
4. Salts					
Al salt I	Prepared by heating an	530	16.5	58.4	
Al salt II	intimate mixture of	600	8.0	51.5	
Ce salt I	ammonium heptamolybdate	560	2.3	39.3	
Ce salt II	and the respective nitrate	600	5.7	45.7	
Zr salt I	(see Experimental	600	5.7	55.6	
Zr salt II	Section).	600	0.7	55.6	

Note. Salt I prepared by heating mixtures of ammonium heptamolybdate and the respective nitrates. Salt II obtained by steaming salt I at 600°C for several hours.

zirconium hydroxide from a solution of zirconyl nitrate by adding ammonia up to pH 9 (16) and calcining the hydroxide at 380°C for 2 h. A high-surface-area sample of MoO₃ was prepared by precipitating ammonium molybdate from an aqueous solution of the heptamolybdate by addition of acetone, drying at 100°C, pressing, and calcining by slowly raising the temperature to 330°C in not less than 6 h (17).

The monolayer catalysts were prepared by adsorption of molybdate ions from an aqueous solution of 1% ammonium heptamolybdate acidified with nitric acid to pH 1 (18). In each case the support was pressed (generally 20–40 tons cm⁻²) and ground to particles of a diameter between 0.3 and 0.5 mm. These catalysts will be referred to as MoO_x/Al₂O₃, etc.

The salts were prepared by heating a mixture of ammonium heptamolybdate and

the respective metal nitrates. The results and a summary of the methods of preparation are given in Table 1. The salt thus obtained is designated as "salt I" which, when treated with steam at 600°C for several hours, gives "salt II."

Apparatus

A fixed-bed flow reactor operating at atmospheric pressure was used to study the reaction. The reactor consisted of a quartz U-tube (50 cm long, 0.5 cm i.d.) with a sintered quartz disc at the lower end of one limb upon which the catalyst was placed. In order to avoid adverse thermal effects the catalysts (0.25 g) were diluted with about two volumes of inert quartz of the same particle size (i.e., 0.3–0.6 mm). The height of the catalyst bed varied between 3 and 5 mm depending on the sample. The reactor was placed vertically inside a tubular fur-

nance heated electrically and controlled within $\pm 1^\circ\text{C}$. The reactor was continuously fed with toluene vapour generated by passing He or a He-O₂ mixture through two saturators in series, one at room temperature and the other at -3.5°C .

Poisoning experiments were carried out by introducing pulses of 0.2 to 2.0 μl of pyridine into the reactant gas stream. The conversion² and selectivity³ were measured as a function of time, temperature, and partial pressure of oxygen.

Analysis

A Becker gas chromatograph equipped with a flame ionization detector was used for the determination of benzene, toluene, and benzaldehyde. The glc column consisted of a 2-m-long copper tube (2 mm i.d.) packed with 5% Apiezon L on Chromosorb wax and operated with He (50 ml/min) as the carrier gas at 155°C . Since benzoic acid could not be separated by this arrangement it was estimated from the carbon balance. This is justified by the fact that under no circumstances was any carbon loss by coke formation observed and benzoic acid was the only oxidation product which could not be determined. CO₂ was estimated by a nonaqueous titration method (19). Draeger tubes were used for the detection of carbon monoxide.

The molybdenum contents of the catalysts were determined by X-ray fluorescence spectroscopy. The surface areas of the samples were measured with an automatic BET apparatus. Argon ($\phi = 13.8 \text{ \AA}^2$) was used as the adsorbate at liquid nitrogen temperature.

RESULTS

1. Catalyst Preparation

In Table 1 the conditions for salt forma-

² Conversion (%) = (No. of moles of toluene oxidized \times 100)/No. of moles of toluene passed.

³ Selectivity (%) = (No. of moles of particular product formed \times 100)/No. of moles of toluene converted.

tion and some properties of all catalysts are given. In the case of monolayer catalysts, the amounts of molybdenum oxide maximally adsorbed on the supports were normally found to be proportional to their surface areas which remained virtually unaltered by the adsorption of molybdenum oxide (see Table 1). Preparation of salts by heating the respective oxides above 700°C ensures purity (i.e., freedom from MoO₃), but only with almost total loss of surface area. Consequently, the molybdate salts were prepared as pure as possible and at such a temperature that a reasonable surface area was still retained. However, the XRD data of these salts showed the presence of some crystallites of MoO₃. Therefore, the catalytic activities were also measured of salts which were completely free from MoO₃ crystals (as indicated by XRD data) by steaming at 600°C . Titanium molybdate could not be prepared by heating a mixture of titanium nitrate and ammonium heptamolybdate, in agreement with the findings of Doyle *et al.* (20).

2. Activity and Selectivity

The conversion of toluene to different products, except for benzaldehyde in the case of MoO_x/CeO₂ and MoO_x/ZrO₂, decreases during approximately the first half hour. This is true for all molybdenum-containing catalysts. The steady state is reached within 40 min. No decrease in the activity has been observed thereafter up to at least 30 h. All kinetic data were taken under steady-state conditions. Low conversions of the reactants (toluene: <20%, oxygen: <9%) enabled the reactor to be considered as working differentially.

The areal activities (i.e., toluene conversion per square meter per unit of time) and selectivities of various monolayer catalysts have been plotted as a function of temperature in Figs. 1 and 2. The order of activities is reflected by the temperature range necessary to obtain a few percent conversion (see Table 2). The general trend is that activities decrease in the order: support

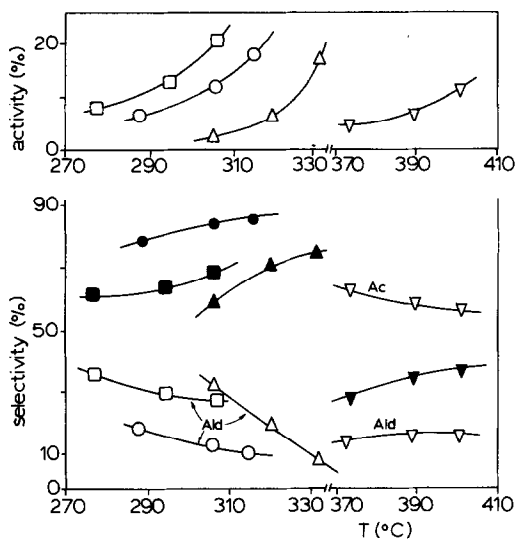


FIG. 1. Activities and selectivities for the toluene oxidation of some molybdenum oxide monolayer catalysts and of Al-molybdate salt as a function of temperature. (\square) $\text{MoO}_x/\text{CeO}_2$; (\circ) $\text{MoO}_x/\text{TiO}_2$; (Δ) $\text{MoO}_x/\text{Al}_2\text{O}_3$; (∇) Al-molybdate. Ald = benzaldehyde; Ac = benzoic acid; black points = total oxidation.

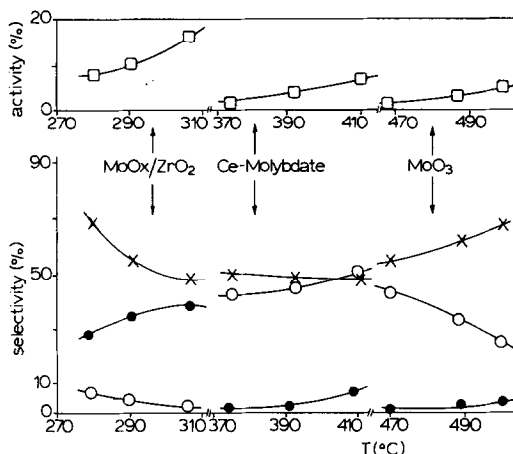


FIG. 2. Activities and selectivities for the toluene oxidation on $\text{MoO}_x/\text{ZrO}_2$, Ce molybdate and crystalline MoO_3 as a function of temperature. (\square) Conversion per m^2 ; (\circ) benzaldehyde; (\times) benzoic acid; (\bullet) total oxidation to CO_2 .

oxides \geq monolayer catalysts $>$ salts $>$ crystalline MoO_3 . In addition to the detailed information on the selectivities in

TABLE 2

Oxidation of Toluene, Activity Level, and Product Distribution of Various Catalysts

Catalyst	Temp. range ^a (°C)	Product Distribution			
		$\text{C}_6\text{H}_5\text{CHO}$	$\text{C}_6\text{H}_5\text{COOH}$	C_6H_6	CO_2
1. Monolayer catalysts					
$\text{MoO}_x/\text{CeO}_2$	275–306	+	--	--	++
$\text{MoO}_x/\text{ZrO}_2$	279–306	-	++	--	+
$\text{MoO}_x/\text{TiO}_2$	288–315	+	-	--	++
$\text{MoO}_x/\text{Al}_2\text{O}_3$	306–336	+	-	-	++
2. Salts					
Al salt II	374–401	+	++	-	+
Ce salt I	374–410	+	+	-	-
Ce salt II	425–454	++	+	-	-
Zr salt II	374	+	++	-	+
3. Pure oxides					
CeO_2	Up to 340	nil	nil	nil	+++
Al_2O_3	Up to 400	nil	nil	nil	+++
TiO_2	306–333	nil	nil	nil	+++
ZrO_2	336–375	nil	nil	-	+++
MoO_3	468–500	+	++	-	-

Note. +++ practically complete oxidation to CO_2 , $> 80\%$ selectivity; ++ major product, 50–80% selectivity; + minor product, 10–50% selectivity; - small amount, 1–10% selectivity; -- trace amount, $< 1\%$ selectivity.

^a Temperature necessary for the conversion of 3–10% of toluene, when $60 \text{ cm}^3 \text{ min}^{-1}$ are led over 0.25 g catalyst; $P_{\text{O}_2} = 0.166 \text{ atm}$; $P_{\text{t}} = 7.1 \cdot 10^{-3} \text{ atm}$.

Figs. 1 and 2, a general survey of the product distribution is given in Table 2. With respect to both activity and selectivity, crystalline MoO_3 resembles the salts more than the monolayer catalysts. This similarity is not, however, due to the presence of traces of MoO_3 crystals left on the salts, as is apparent by the behaviour of the steam-treated salts. Although the catalytic activities of the salts were lowered to some extent by treatment with steam at 600°C , the selectivities hardly changed.

The colour of the monolayer catalysts changed from light yellow to dark blue when the oxygen/toluene ratio was decreased from 23 to 4. The dark colour is indicative of Mo ions with a valency lower than 6 and not of coking products, because the treatment of the dark catalysts with oxygen did not yield any oxides of carbon. The colour of the salts, however, was not found to depend on the oxygen/toluene ratio.

A decrease of the oxygen/toluene ratio, as mentioned above, also causes a minor change in the selectivity of the catalysts. For example, the selectivities of $\text{MoO}_x/\text{Al}_2\text{O}_3$ and $\text{MoO}_x/\text{TiO}_2$ at 306°C towards benzaldehyde are larger at higher oxygen/toluene ratios.

3. Poisoning Experiments

These experiments show that a pulse of pyridine at the steady state of toluene oxidation on $\text{MoO}_x/\text{TiO}_2$ causes a sudden decrease in the conversion (Fig. 3). This poisoning is reversible because the decreased conversion increases with time and attains nearly the original value about 25 min after the injection of pyridine. In the poisoned condition, the selectivity for benzaldehyde formation increases to a very high value at the expense of the total oxidation. Figure 3 clearly demonstrates the effect of adsorbed pyridine on the activity and selectivity of a representative molybdenum oxide monolayer catalyst.

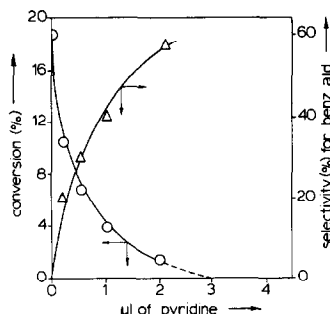


FIG. 3. Activities and selectivities for toluene oxidation on $\text{MoO}_x/\text{TiO}_2$ catalyst at 360°C after poisoning with various amounts of pyridine. Measurements were made 2 min after pyridine injection.

DISCUSSION

Preparation of the Catalysts

The amount of Mo oxide maximally adsorbed per unit surface area of CeO_2 , TiO_2 , and Al_2O_3 from aqueous solutions corresponds well with those reported earlier in the literature (18, 21). Its reciprocal, that is, the area available per Mo^{6+} oxide unit, corresponds to the mean cross-sectional area of a Mo^{6+} oxide unit in crystalline MoO_3 (15.4 \AA^2) (Table 1). This indicates that under the conditions of their formation a practically complete monolayer of Mo oxide is present on the surface of these supports (21). The slightly different behaviour of ZrO_2 might be due to the presence of micropores (16) which are not easily penetrated by the Mo anions during the adsorption stage of preparation.

A suitable method was found for the preparation of Al and Ce salts with a workable surface area and a reasonable purity. Table 1 shows the results. The excess MoO_3 crystals were removed from the freshly prepared salts by steaming at 600°C for several hours.

Activities of the Catalysts

The supports, which are almost exclusively nonselective, influence both the activity and selectivity of MoO_3 , which, in turn, masks or modifies the catalytic properties of the supports. The suppression of

the highly nonselective oxidation property of CeO_2 due to the presence of a monolayer of Mo oxide on the surface is in accord with the property of the Ce-molybdate salt, which also is a highly selective catalyst for the formation of benzaldehyde and benzoic acid (Table 2). Similar behaviour is observed with other monolayer catalysts and salts. Akimoto and Echigoya (13, 22) and Trifirò and Pasquon (12) observed that nonselective oxidation occurs more easily on oxides containing bridged (σ -bonded) oxygen than on double-bonded (π -bonded) oxygen of more acidic oxides. The present findings substantiate this. The activity and selectivity patterns, therefore, indicate the presence of only a small amount of support oxide units with bridged oxygen on the surface of the monolayer catalysts and an even smaller amount of these units on the surface of the salts. It is also clear from these results that the more active catalysts are more conducive to the total oxidation of toluene. The activity trend, supports \cong monolayer catalysts $>$ salts $>$ MoO_3 , is exactly opposite to the selectivity trend.

Kinetics

The change in colour of the monolayer catalysts associated with decreased oxygen/toluene ratio and the ability of the fresh catalysts to oxidize toluene in the absence of gaseous oxygen indicate that the reaction proceeds via the consumption of lattice oxygen of the surface and reoxidation of the reduced sites. Therefore, the rate equation, based on the assumption of a redox mechanism (23), was applied to the rate data, namely,

$$r^{-1} = \frac{\alpha}{k_0 P_{\text{O}_2}^n} + \frac{1}{k_r P_t^m}, \quad (1)$$

where r is the reaction rate (moles of toluene $\text{min}^{-1} \text{m}^{-2}$), k_0 and k_r are the rate constants for the oxidation of the reduced sites and for the reduction of the oxidized sites, P_{O_2} and P_t are the partial pressures of oxygen and toluene (atm), n and m are the reaction orders, α is the average num-

ber of oxygen molecules consumed in oxidizing one molecule of toluene to the various products. The linearized equation with $n = m = 1$,

$$\frac{P_{\text{O}_2}}{r} = \frac{\alpha}{k_0} + \frac{P_{\text{O}_2}}{k_r P_t} \quad (2)$$

was found to be applicable to the rate data of all catalysts. The values of α have been calculated from the product distribution and are between 4.0 and 8.1 for the monolayer catalysts, 9.0 for the supports, about 2.5 for MoO_3 , and between 2.2 and 4.9 for the salts. Figure 4 demonstrates the applicability of this equation to the rate data. The kinetic parameters were calculated from Arrhenius plots and are given in Table 3.

A change in catalyst composition leads to two important observations relative to the kinetic parameters, namely, (a) an inverse relation between the values of E_0 and E_r and (b) a strong compensation effect between E_0 and A_0 and between E_r and A_r (A_0 and A_r

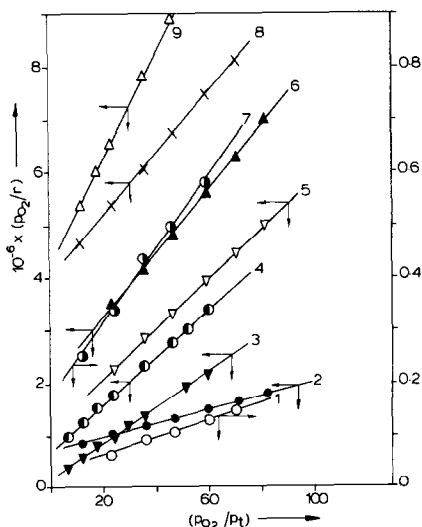


FIG. 4. Demonstration of the validity of rate equation (2) for toluene oxidation. $P_t = 0.007$ atm, $0.04 < P_{\text{O}_2} < 0.7$ atm. Rates are expressed in moles $\text{min}^{-1} \text{m}^{-2}$. 1. Ce salt I at 410°C ; 2. $\text{MoO}_x/\text{TiO}_2$ at 306°C ; 3. $\text{MoO}_x/\text{CeO}_2$ at 306°C ; 4. $\text{MoO}_x/\text{ZrO}_2$ at 306°C ; 5. TiO_2 at 306°C ; 6. Al salt II at 374°C ; 7. Ce salt II at 454°C ; 8. ZrO_2 at 350°C ; 9. $\text{MoO}_x/\text{Al}_2\text{O}_3$ at 306°C .

TABLE 3

Activation Energies and Preexponential Factors of the Oxidation and the Reduction Steps of Toluene Oxidation on Various Catalysts

Catalyst	E_o (kJ · mole ⁻¹)	E_r (kJ · mole ⁻¹)	A_o (Mole · min ⁻¹ · m ⁻² · atm ⁻¹)	A_r (mole · min ⁻¹ · m ⁻² · atm ⁻¹)
MoO ₃ /CeO ₂	168.4	74.3	1.8 × 10 ⁷	3.1 × 10 ²
MoO ₃ /ZrO ₂	120.5	128.5	7.1 × 10 ³	1.0 × 10 ²
MoO ₃ /TiO ₂	93.7	180.2	5.6 × 10 ¹	1.8 × 10 ⁰
MoO ₃ /Al ₂ O ₃	80.6	187.7	3.1 × 10 ¹	6.3 × 10 ⁷
Ce salt I	153.3	81.5	2.0 × 10 ⁶	2.2 × 10 ⁴
Ce salt II	229.8	120.1	2.0 × 10 ¹¹	1.4 × 10 ⁵
Al salt II	121.0	121.0	8.9 × 10 ⁵	8.9 × 10 ⁵
Pure TiO ₂	50.0	160.9	6.3 × 10 ⁰	7.8 × 10 ⁶
Pure ZrO ₂	121.0	49.1	1.0 × 10 ³	1.0 × 10 ⁻³
MoO ₃	210.7	62.2	1.0 × 10 ⁷	3.1 × 10 ⁵

are the preexponential factors in the Arrhenius equation.)

(a) This observation may have the background that an increase in the binding energy between the active oxygen and the Mo ion hinders the removal (reflected by the higher value of E_r) of the former by toluene and facilitates (shown by a lower value of E_o) the uptake of oxygen by the reduced catalyst.

There is also a correlation of E_o and E_r with the ionic potential, z/r , (i.e., the ratio of charge and radius) of the support cations of the monolayer catalysts (Fig. 5). This means that high-valent and small-sized support cations cause an increase in E_r for the

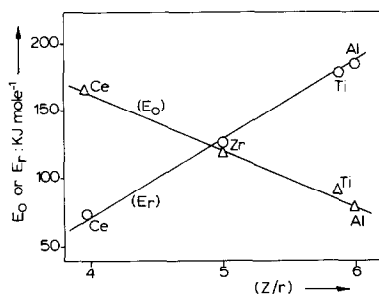


FIG. 5. Correlations of the activation energies of the oxidation (E_o) and reduction (E_r) steps of toluene oxidation on the various molybdenum oxide monolayer catalysts with the ionic potentials of the respective support ions (using Pauling ionic radii).

oxidation of toluene on the molybdenum oxide monolayer catalysts. The reaction mechanism assumed for this type of composite catalyst embodies the adsorption of toluene and abstraction of a H atom from the methyl group by an acid site and attachment of the benzyl radical to a basic site (3, 14, 24, 25). This adsorbed benzyl radical is subsequently oxidized partially or totally depending upon the nature of the catalyst. From a theoretical point of view, as well as from the experimental observations of Sachtler *et al.* (26), the value of E_r can be inversely correlated with Mo=O bond strength. All the above information suggests, therefore, that the bond strength of the active oxygen on the molybdenum oxide monolayer catalysts increases with increasing ionic potential of the cations of the supporting oxides.

(b) The compensation effect is illustrated in Fig. 6 for all the catalysts used. Mann (27) observed the same effect with various oxidation and isotope exchange reactions on doped and undoped vanadium oxide catalysts. The wide difference in the values of A_o and A_r , as observed from Table 3, cannot stem primarily from the changes in the entropies of activation and reaction entropies of the established equilibria (28). The large change in the ratio of the values

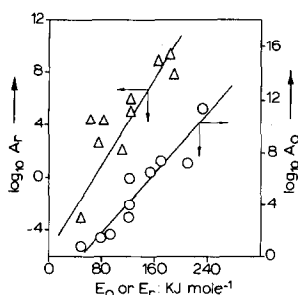


FIG. 6. The compensation effect of the oxidation (O) and reduction (Δ) steps of the oxidation of toluene. A_0 and A_r are expressed in $\text{moles min}^{-1} \text{m}^{-2} \text{atm}^{-1}$. The correlation coefficients with respect to the oxidation and reduction steps are +0.93 and +0.79, respectively.

of A_0 and A_r with different catalysts suggests that molecular oxygen, during the reoxidation step of the redox cycle, does not adsorb directly on all anion vacancies (29) created by toluene during its oxidation. This means, therefore, that toluene reacts (at least partly) with $\text{Mo}=\text{O}$ sites which are not directly oxidized by gaseous oxygen during the reoxidation step of the reduced catalyst pertaining to the redox mechanism.

The results of poisoning experiments with pyridine give some idea of the nature and concentration of the active sites on the molybdenum oxide monolayer catalysts. Total, albeit transient, loss of activity of $\text{MoO}_x/\text{TiO}_2$ seems to take place by the adsorption of about $3 \mu\text{l}$ of pyridine on 0.25 g of the catalyst (Fig. 3). This corresponds to a pyridine/Mo ratio of about 0.3 and suggests that for the monolayer catalysts the number of active sites is approximately one-third of the number of Mo ions present of the surface.

The Selectivities of the Catalysts

The relative rate of the formation of CO_2 on the supports is much higher than on the molybdenum oxide monolayer catalysts and is practically negligible on crystalline MoO_3 and most of the salts. The nearly identical behaviour of the salts and crystalline MoO_3 (see Table 2) suggests that either the activity and selectivity of the salts are mainly due to the MoO_3 crystals present on

the surface or alternatively, that the species formed on the surface of the salts by the interaction of $\text{Mo}=\text{O}$ and the support oxide units have similar catalytic properties to crystalline MoO_3 . Since it has already been seen from the behaviour of steamed and unsteamed salts that this similarity is not due to the excess MoO_3 crystals on the surface, the second explanation is preferred.

The oxidation properties of the monolayer catalysts and the salts demonstrate an inverse relationship between activity and selectivity. This kind of phenomenon has also been reported in the literature (5). It is noteworthy that the selective properties neither of the monolayer catalysts nor of the salts are a function of the foreign ion.

The increase in selectivity for the production of benzaldehyde at the expense of CO_2 (Fig. 6) on a pyridine-poisoned monolayer catalyst is in harmony with the observation of Akimoto and Echigoya (22) that the total oxidation of butadiene on a pyridine-poisoned MoO_3 catalyst supported on Al_2O_3 diminishes considerably as compared with the unpoisoned catalyst. It is also known that the total oxidation of aromatic hydrocarbons on vanadium-oxide-containing catalysts is suppressed by the presence of traces of alkali metal ions. Therefore, the general conclusion is that the total oxidation (to CO_2) is connected with relatively strong acid sites. Obviously, their strength would decide whether oxygen should attack the methyl group or the aromatic nucleus to yield predominant amounts of partial oxidation products or CO_2 , respectively.

CONCLUSIONS

1. The activities of the various groups of catalysts reported here for the oxidation of toluene decrease in the order: support oxides \approx molybdenum oxide monolayer catalysts $>$ molybdate salts $>$ crystalline molybdenum oxide. The selectivities for partial oxidation products follow exactly the opposite trend.

2. A relatively small number of support oxide units (with σ -bonded bridged oxygen) appear to be present on the surface of the molybdenum oxide monolayer catalysts and an even smaller number on the molybdate salts.

3. The bond strength of the active oxygen units on the monolayer catalysts increase with increasing ionic potential of the support oxide upon which the molybdenum oxide monolayers are formed.

4. There is a strong indication that the oxidation of the reduced active sites does not occur by the direct attack of gaseous oxygen on the sites during the reoxidation step.

5. The total oxidation of toluene to CO₂ occurs on relatively strong acid sites on the catalyst surface.

6. The number of active sites on the molybdenum oxide monolayer catalysts is approximately one-third of the number of Mo ions present on the surface.

ACKNOWLEDGMENTS

One of us (N. K. Nag) thanks the Akzo-Chemie Netherlands B. V. and the Twente University for a fellowship during 1976. Thanks are also due to J. Boeijisma and F. Roozeboom for their assistance in some of the experimental work, and to P. J. Gellings for his comments.

REFERENCES

- Buiten, J., *J. Catal.* **21**, 188 (1968).
- Tan, S., Moro-oka, Y., and Ozaki, A., *J. Catal.* **17**, 125 and 132 (1970).
- Ai, M., and Ikawa, T., *J. Catal.* **40**, 203 (1975).
- Batist, Ph. A., Der Kinderen, A. H. W. M., Leeuwenburgh, Y., Metz, F. A. M. G., and Schuit, G. C. A., *J. Catal.* **12**, 45 (1968).
- Boreskov, G. K., in "Proceedings, 3rd International Congress on Catalysis, Amsterdam, 1964," p. 163. North-Holland, Amsterdam, 1965.
- Gelbshetin, A. J., Stroeve, S. S., Bakshi, Yu. M., and Mischenko, Yu. A., in "Proceedings, 4th International Congress on Catalysis, Moscow, 1968" (B. A. Kazansky, Ed.), Vol. I, p. 297. Akadémiai Kiadó, Budapest, 1971.
- Boreskov, G. K., in "Advances in Catalysis and Related Subjects," Vol. 15, p. 309. Academic Press, New York/London, 1965.
- Sachtler, W. H. M., and De Boer, N. H., in "Proceedings, 3rd International Congress on Catalysis, Amsterdam, 1964," p. 252. North-Holland, Amsterdam, 1965.
- Baryshevskay, I. M., and Gorokhahalis, B., *React. Kinet. Catal. Lett.* **5**, 337 (1976).
- Pernicone, N., Liberti, G., and Ersini, L., in "Proceedings, 4th International Congress on Catalysis Moscow, 1968" (B. A. Kazansky, Ed.), Vol. I, p. 287. Akadémiai Kiadó, Budapest, 1971.
- Cornaz, P. F., Van Hooff, J. H. C., Pluym, F. J., and Schuit, G. C. A., *Discuss. Faraday Soc.* **41**, 290 (1966).
- Trifirò, F., and Pasquon, I., *J. Catal.* **12**, 412 (1968).
- Akimoto, M., and Echigoya, E., *J. Catal.* **29**, 191 (1973).
- Haber, J., and Grzybowska, B., *J. Catal.* **28**, 489 (1973).
- Potman, W., Van Ommen, J. G., and Dahmen, E. A. M. F., *Mikrochim. Acta (Wien)* **1**, 633 (1975).
- Rijnten, H. Th., in "Physical and Chemical Aspects of Adsorbents and Catalysts" (B. C. Linsen, Ed.). Academic Press, London/New York, 1970.
- Fransen, T., Van Berge, P. C., and Mars, P., *React. Kinet. Catal. Lett.* **5**, 445 (1976).
- Sonnemans, J., and Mars, P., *J. Catal.* **31**, 209 (1973).
- Jones, R. F., Gale, P., Hopkins, P., and Powell, L. N., *Analyst* **90**, 623 (1965).
- Doyle, W. P., McGuire, G., and Clark, G. M., *J. Inorg. Nucl. Chem.* **28**, 1185 (1966).
- Fransen, T., Van Berge, P. C., and Mars, P., in "Preparation of Catalysts" (B. Delmon, P. A. Jacobs, and G. Poncelet, Eds.), p. 405. Elsevier, Amsterdam, 1976.
- Akimoto, M., and Echigoya, E., *J. Catal.* **31**, 278 (1973).
- Mars, P., and Van Krevelen, D. W., *Chem. Eng. Sci. Suppl.* **3**, 41 (1954).
- Godin, G. W., McLain, C. C., and Porter, E. H., in "Proceedings, 4th International Congress on Catalysis Moscow, 1968," Vol. I, p. 271. Akadémiai Kiadó, Budapest, 1971.
- Sachtler, W. M. H., *Catal. Rev. Sci. Eng.* **4**, 27 (1968).
- Sachtler, W. H. M., Dorgelo, G. J. H., Fahrenfort, J., and Voorhoeve, R. J. H., *Recueil* **89**, 460 (1970).
- Mann, R. F., *Canad. J. Chem.* **49**, 1520 (1971).
- Baetzold, R. C., and Somorjai, G. A., *J. Catal.* **45**, 94 (1976).
- Keulks, G. W., *J. Catal.* **19**, 232 (1970).