

Preparation and Solid State Characterization of 1,2,3,5-Diselenadiazolyl [HCN₂Se₂][•]A. Wallace Cordes,^a Sivert H. Glarum,^b Robert C. Haddon,^b Randal Hallford,^a Robin G. Hicks,^c Dietmar K. Kennepohl,^c Richard T. Oakley,^c Thomas T. M. Palstra^b and Syrona R. Scott^a^a Department of Chemistry and Biochemistry, University of Arkansas, Fayetteville, Arkansas 72701, USA^b AT & T Bell Laboratories, 600 Mountain Avenue, Murray Hill, New Jersey 07974, USA^c Guelph-Waterloo Centre for Graduate Work in Chemistry, Guelph Campus, Department of Chemistry and Biochemistry, University of Guelph, Guelph, Ontario N1G 2W1, Canada

The reaction of *N,N,N'*-tris(trimethylsilyl)formamidine with SeCl₂ affords 1,2,3,5-diselenadiazolium chloride, which can be reduced with triphenylantimony to the corresponding diselenadiazolyl radical [HCN₂Se₂][•]; the solid state structure and conductivity of the dimer [HCN₂Se₂]₂ are reported.

Interest in the design of molecular conductors based on neutral π -radicals has prompted the study of heterocyclic thiazyl and selenazyl radicals, in particular derivatives of 1,2,3,5-dithia- and diselena-diazolyl.¹ Several systems with different substituents in the 4-position have been characterized in the solid state.^{2,3} Structure-conductivity correlations based on several selenium derivatives⁴⁻⁶ indicate that the size of the 4-substituent plays an important role in determining the number and magnitude of close intermolecular interactions, and hence band dispersion.⁷ In the belief that smaller organic substituents should lead to more densely-packed structures with narrower band gaps, we have prepared the prototypal diselenadiazolyl heterocycle **1**, in which the organic group has been removed entirely. The solid state characterization of the dimer is also described.

Our primary synthetic route to both 1,2,3,5-dithia- and diselena-diazolium cations has involved the condensation of persilylated amidines RCN(SiMe₃)₂NSiMe₃ with ECl₂ (E = S, Se). However, the method of preparation of the amidines, the addition of LiN(SiMe₃)₂ to a nitrile RCN,⁸ appears to be limited to aryl nitriles. We have now discovered that the parent compound *N,N,N'*-tris(trimethylsilyl)formamidine **2** can be conveniently generated by the reaction of LiN(SiMe₃)₂·Et₂O (54.1 g, 224 mmol) with 1,3,5-triazine (6.2 g, 76 mmol) in 200 ml toluene, followed by treatment of the intermediate lithiated amidine with Me₃SiCl (25.7 g, 237 mmol); **2** distils at 35 °C/10⁻² Torr (1 Torr = 133.3 Pa; yield, 41.5 g, 66%); ¹H NMR, δ (CDCl₃) 7.96 (s, 1 H, HC), 0.16 (s, 27 H, Me₃Si). Addition of **2** (6.38 g, 24 mmol) to selenium dichloride (3.60 g, 24 mmol, prepared *in situ* from Se and SeCl₄) in acetonitrile (140 ml) affords the diselenadiazolium cation **3** (E = Se) as a reddish-brown powder in virtually quantitative yield. Reduction of this crude salt (1.27 g, 5.4 mmol) with triphenylantimony (0.96 g, 2.7 mmol) in acetonitrile (20 ml) yields 1,2,3,5-diselenadiazolyl **1**, which can be purified by sublimation at 50 °C/10⁻³ Torr as lustrous grey-black needles (0.56 g, 52%); decomp. > 100 °C; MS (70 eV) *m/z* 201 (M⁺, 40%), 174 (Se₂N⁺, 95%), 160 (Se₂⁺, 100%), 107 (HCNSe⁺, 8%), 94 (SeN⁺, 20%), 80 (Se⁺, 50%). The ESR signal (in CH₂Cl₂, 295K) of **1** consists of a featureless singlet, with *g* = 2.041.

The crystal structure of the dimer of **1** has been determined by X-ray diffraction.[†] The structure consists of antiparallel arrays of cofacial dimers [HCN₂Se₂]₂; Fig. 1 provides a general view of the structure, defines the interdimer contacts *d*₁-*d*₆, and illustrates the head-over-tail packing of dimers. All intramolecular bond lengths and angles are nominal, but the two interannular contacts Se(1)⋯Se(3) [3.215(3) Å] and Se(2)⋯Se(4) [3.345(3) Å] are notably different (*cf.* [PhCN₂Se₂]₂³). The interdimer Se⋯Se contacts *d*₅ and *d*₆ are well within the van der Waals separation,⁹ and generate a strong network of lateral interactions. These lateral contacts help lace together interpenetrating spiral-like columns of dimers, one of which is shown in Fig. 2. Within these columns, which run parallel to *z*, there are many close Se⋯Se contacts. The interactions *d*₁, *d*₂ and *d*₄, which connect dimer units that approach one another in a side-slipped head-on manner, are all exceptionally short. The final contact *d*₃ runs almost parallel to *z* and connects (somewhat loosely) rings in a corner-to-corner fashion.

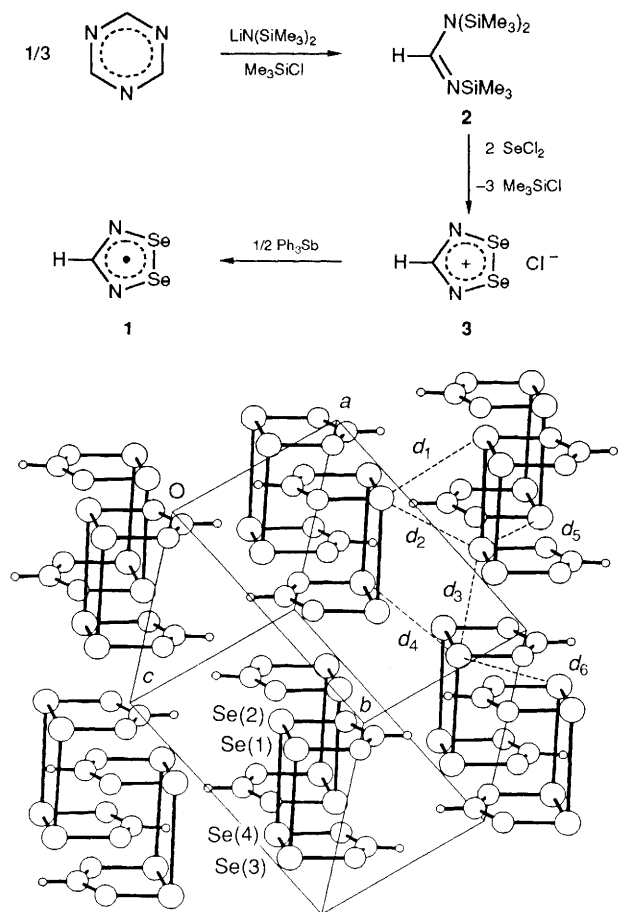


Fig. 1 General view of the crystal structure of [HCN₂Se₂]₂, showing head-over-tail stacking of dimers. Intradimer distances (Å) are Se(1)-Se(2) 2.329(4); Se(3)-Se(4) 2.322(4); Se(1)-Se(3) 3.215(3); Se(2)-Se(4), 3.345(3); interdimer contacts (Å) are *d*₁, Se(4)⋯Se(2') 3.382(4); *d*₂, Se(4)⋯Se(4'), 3.376(5); *d*₃, Se(1)⋯Se(4'), 4.049(4); *d*₄, Se(1)⋯Se(1'), 3.445(5); *d*₅, Se(2)⋯Se(4') 3.724(4); *d*₆, Se(1)⋯Se(3'), 3.774(5).

[†] Crystal data for **1**: Se₂N₂CH, *M* = 199.0, triclinic, *P* $\bar{1}$, *a* = 6.279(4), *b* = 7.961(6), *c* = 8.012(5) Å, α = 69.94(6), β = 88.98(5), γ = 84.03(6)°, *V* = 374.1(4) Å³, *Z* = 4, *D*_c = 3.53 g cm⁻³, μ = 19.4 mm⁻¹. Data were collected with an Enraf-Nonius CAD-4 automated diffractometer, with graphite-monochromated Mo-K α -radiation (λ = 0.71073 Å) using θ - 2θ scans to a $2\theta_{\max}$ = 50°. The structure was solved by direct methods (SHELX) and refined by full-matrix least-squares analysis which minimized $\sum w(F_o - F_c)^2$. 81 Parameters were refined using 700 unique observed reflections [*I* > 2.5 σ (*I*)] to give *R* = 0.048 and *R*_w = 0.050. Atomic coordinates, bond lengths and angles, and thermal parameters have been deposited at the Cambridge Data Centre. See Notice to Authors, Issue No. 1.

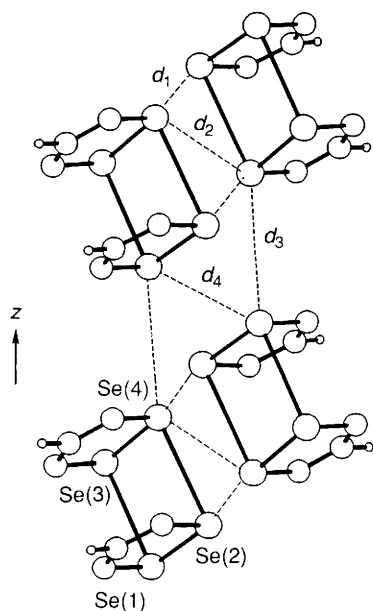


Fig. 2 Columns of dimers running parallel to z

In the solid state the dimer $[\text{HCN}_2\text{Se}_2]_2$ is diamagnetic, with a residual spin density, estimated by ESR, of 0.01%. The material exhibits a single crystal conductivity of $7 \times 10^{-6} \text{ S cm}^{-1}$, a value which is at least three orders of magnitude higher than that seen in other monofunctional selenium-based radical dimers.⁴ Collectively the interdimer $\text{Se} \cdots \text{Se}$ contacts, indicated above, generate a structure in which dispersion of the valence and conduction bands is more pronounced than in organo-substituted materials.

We thank the NSERC of Canada, the NSF and the State of Arkansas for financial support.

Received, 13th May 1992; Com. 2/02481K

References

- 1 A. W. Cordes, R. C. Haddon and R. T. Oakley, in *The Chemistry of Inorganic Ring Systems*, ed. R. Steudel, Elsevier, Amsterdam, 1992, p. 295; (b) A. J. Banister and J. M. Rawson, in *The Chemistry of Inorganic Ring Systems*, ed. R. Steudel, Elsevier, Amsterdam, 1992, p. 323.
- 2 A. Vegas, A. Pérez-Salazar, A. J. Banister and R. G. Hey, *J. Chem. Soc., Dalton Trans.*, 1980, 1812; H.-U. Hofs, J. W. Bats, R. Gleiter, G. Hartmann, R. Mews, M. Eckert-Maksić, H. Oberhammer and G. M. Sheldrick, *Chem. Ber.*, 1985, **118**, 3781; A. W. Cordes, J. D. Goddard, R. T. Oakley and N. P. C. Westwood, *J. Am. Chem. Soc.*, 1989, **111**, 6147; A. J. Banister, M. I. Hansford, Z. V. Hauptmann, S. T. Wait and W. Clegg, *J. Chem. Soc., Dalton Trans.*, 1989, 1705.
- 3 P. Del Bel Belluz, A. W. Cordes, E. M. Kristof, P. Kristof, S. W. Liblong and R. T. Oakley, *J. Am. Chem. Soc.*, 1989, **111**, 9276.
- 4 A. W. Cordes, R. C. Haddon, R. G. Hicks, R. T. Oakley and T. T. M. Palstra, *Inorg. Chem.*, 1992, **31**, 1802.
- 5 A. W. Cordes, R. C. Haddon, R. T. Oakley, L. F. Schneemeyer, J. V. Waszczak, K. M. Young and N. M. Zimmerman, *J. Am. Chem. Soc.*, 1991, **113**, 582.
- 6 M. P. Andrews, A. W. Cordes, D. C. Douglas, R. M. Fleming, S. H. Glarum, R. C. Haddon, P. Marsh, R. T. Oakley, T. T. M. Palstra, L. F. Schneemeyer, G. W. Trucks, R. Tycko, J. V. Waszczak, K. M. Young and N. M. Zimmerman, *J. Am. Chem. Soc.*, 1991, **113**, 3559.
- 7 A. W. Cordes, R. C. Haddon, R. G. Hicks, R. T. Oakley, T. T. M. Palstra, L. F. Schneemeyer and J. V. Waszczak, *J. Am. Chem. Soc.*, 1992, **114**, 1729.
- 8 R. T. Boeré, R. T. Oakley and R. W. Reed, *J. Organomet. Chem.*, 1987, **331**, 161.
- 9 A. Bondi, *J. Phys. Chem.*, 1964, **68**, 441.